

## Original Article

# Effect of bracket bonding with Er:YAG laser on nanomechanical properties of enamel

Shiva Alavi<sup>1</sup>, Reza Birang<sup>2</sup>, Fatemeh Hajizadeh<sup>3</sup>, Hamed Banimostafae<sup>4</sup>

<sup>1</sup>Dental Materials Research Center and Department of Orthodontics, <sup>2</sup>Torabinejad Dental Research Center and Department of Periodontics, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, <sup>3</sup>Department of Orthodontics, School of Dentistry, Ahvaz Jundishapur University of Medical Sciences, Ahvaz, <sup>4</sup>Department of Orthodontics, School of Dentistry, Arak University of Medical Sciences, Arak, Iran.

## ABSTRACT

**Background:** The aim of this study was to compare the effects of conventional acid etching and laser etching on the nano-mechanical properties of the dental enamel using nano-indentation test.

**Materials and Methods:** In this experimental *in vitro* study, buccal surfaces of 10 premolars were divided into three regions. One of the regions was etched with 37% phosphoric acid and another etched with Er:YAG laser, the third region was not etched. The brackets were bonded to both of etched regions. After thermocycling for 500 cycles, the brackets were removed and the teeth were decoronated from the bracket bonding area. Seven nano-indentations were applied at 1-31  $\mu\text{m}$  depth from the enamel surface in each region. Mean values of the hardness and elastic modulus were analyzed with repeated measures analysis of variance and Tukey HSD tests, using the SPSS software (SPSS Inc., version 16.0, Chicago, IL, USA).  $P < 0.05$  was considered as significant.

**Results:** The hardness up to 21  $\mu\text{m}$  in depth and elastic modulus up to 6  $\mu\text{m}$  in depth from the enamel surface for laser-etched enamel had significantly higher values than control enamel and the hardness up to 11  $\mu\text{m}$  in depth and elastic modulus up to 6  $\mu\text{m}$  in depth for acid-etched enamel had significantly lower values than the control enamel.

**Conclusion:** The mechanical properties of the enamel were decreased after bracket bonding with conventional acid etching and increased after bonding with Er:YAG laser.

**Key Words:** Elastic modulus, enamel, Er:YAG laser, hardness, nano-indentation test, orthodontic bracket

Received: February 2013

Accepted: June 2013

### Address for correspondence:

Dr. Fatemeh Hajizadeh,  
Department of  
Orthodontics, School  
of Dentistry, Ahvaz  
Jundishapur University of  
Medical Sciences, Golestan  
Street, Ahvaz, Postal Code:  
6135715775, Iran.  
E-mail: hajizadeh\_fatemeh  
@yahoo.com

## INTRODUCTION

The basis for the bonding of brackets to enamel has been enamel etching with phosphoric acid, which was first introduced by Buonocore in 1955.<sup>[1]</sup> Now orthodontists have successfully bonded the orthodontic appliances in offices around the world for about 40 years. However, a potential disadvantage of enamel acid etching is the demineralization of the superficial layer, which leaves

the enamel more susceptible to the white-spot formation and caries, especially under orthodontic attachments.<sup>[2]</sup>

Various preparation methods including maleic and polyacrylic acids, sandblasting and laser ablation have been suggested to etch enamel for orthodontic bonding.<sup>[3-5]</sup> Sandblasting and polyacrylic acid have been applied to control the enamel loss, but they have resulted in reduced bond strength on enamel.<sup>[6-8]</sup>

Thus, Er:YAG laser could be a suitable alternative for phosphoric acid because previous studies have cited that bonding strength was similar in groups etched either by acid or laser.<sup>[9-12]</sup>

The first application of laser in dentistry was reported in 1964, which was used to increase the resistance of enamel to demineralization and prevention of caries.<sup>[13]</sup> Some studies reported that Erbium lasers irradiation

Access this article online



Website: <http://drj.mui.ac.ir>

can decrease acid dissolution and increase fluoride uptake of enamel.<sup>[14,15]</sup> Furthermore, it has been found that Erbium lasers have an antimicrobial effect.<sup>[16]</sup>

Laser etching leads to thermally — induced changes such as melting and recrystallization of the enamel prisms.<sup>[17,18]</sup> It can produce non-specific and mixed-type pattern of the enamel prisms to a depth of 10-20  $\mu\text{m}$ , depending upon the type of laser and its power setting.<sup>[19]</sup>

Apel *et al.*<sup>[20]</sup> in the microscopic examination following laser irradiation reported that the entire enamel surface was covered with fine cracks, extending up to 100  $\mu\text{m}$  depth.

Uşümez *et al.*<sup>[4]</sup> found that the polished surface of the laser-etched samples had a more irregular pattern than that of the polished acid-etched samples with crack-like structures.

Márquez *et al.*<sup>[21]</sup> reported that Knoop hardness was increased after laser application on the enamel. Iijima *et al.*<sup>[22]</sup> showed that acid-etched enamel had significantly lower nano-hardness and elastic modulus values compared with the unetched enamel.

Therefore, recognizing mechanical changes in the microstructural features of enamel after removing orthodontic brackets is important to understand iatrogenic damages, such as enamel fracture or cracks during de-bonding. Recently, the nano-indentation test has become a common technique for measuring mechanical properties such as hardness and elastic modulus in biological hard tissues.<sup>[22-27]</sup>

The purpose of the present study was to evaluate the effects of conventional acid-etching and laser-etching on the nano-mechanical properties of the dental enamel, using nano-indentation test.

## MATERIALS AND METHODS

In this experimental *in vitro* study, ten caries-free, intact human upper premolars, extracted for orthodontic purposes were used. After cleansing the root surface, the teeth were stored in Hank's balanced salt solution (HBSS, Sigma-Aldrich, St. Louis, MO, USA) in order to minimize enamel surface demineralization and subsequent alterations in the nano-mechanical properties of superficial enamel.<sup>[26,28]</sup> Antibiotics (penicillin 100 $\times$ , metronidazole 100 $\times$ , gentamicin 100 $\times$ , amphotericin 100 $\times$ ) with 1% volume ratio were added to HBSS to prevent bacterial growth.

The teeth were embedded in self-cure acrylic resin (Dentsply Ltd., Surrey, England) up to the cemento-enamel junction. For all teeth, buccal enamel surface was cleaned by non-fluoridated pumice and rubber cup, washed and dried before the etching procedure.

The buccal surface was divided into mesial and distal regions using masking tape (approximately 1.5 mm width). One of the regions was randomly etched with phosphoric acid and another with Er:YAG laser. Unetched enamel under the masking tape was assumed as the control region.

### Laser-etched region

An Er:YAG laser (Fotona, fidelis plus, Ljubljana, Slovenia) was used for etching one of the regions on the buccal enamel surface.

This device operates at a wavelength of 2940 nm with 2 watt power and 100 mj energy at 20 Hz, short pulse mode for 20 s. Energy density and power density were calculated 15.72 J/cm<sup>2</sup> and 31.45 W/cm<sup>2</sup> respectively. The laser beam was perpendicular to the enamel surface at a 1 mm distance (contact mode) and was moved in a sweeping fashion by hand. Laser application was performed with sufficient air and water cooling.

### Acid-etched region

Another region was etched with 37% phosphoric acid gel (American orthodontics, Sheboygan, WI, USA) for 15 s, rinsed for 20 s and dried with an oil-free air spray until frosty white appearance was visible.

### Bonding procedure

A thin coating of Transbond XT primer (3M Unitek, Monrovia, CA, USA) was applied on the both prepared regions with a microbrush. Twenty stainless-steel mandibular incisor brackets (American orthodontics, Sheboygan, WI, USA) were bonded with Transbond XT adhesive resin (3M Unitek, Monrovia, CA, USA) onto the mesial and distal etched regions. After removing the excessive resins, the specimens were cured with a light emitting diode (Starlight Pro, Carasco, Italy) for 20 s (10 s from each proximal side).

The masking tape was removed and specimens were immediately stored in distilled water bath at 37°C for 24 h and then were thermocycled for 500 cycles at 5-55°C to simulate the environment of the oral cavity.<sup>[4]</sup>


Afterwards, the metal brackets were deboned and the residual adhesives were removed by a low-speed tungsten carbide bur (REF 123-603-00, Dentaaurum, Ispringen, Germany) and the buccal enamel was polished with non-fluoridated pumice.

Again, the specimens were mounted in acrylic resin blocks so that both control and bonded regions were covered with acrylic resin. The crown of the teeth was sectioned with a slow-speed water-cooled diamond saw (TC3000, Vafaei industrial, Tehran, Iran), at the previously bonded regions and parallel to the occlusal surface. The sliced surface of the cervical half of the crown was polished with a series of silicon carbide abrasive papers up to 4000 grit size to obtain a flat and smooth polished surface for the nano-indentation test. The final polishing was performed with diamond paste (3 and 1  $\mu\text{m}$  particle size). The sliced surfaces were gently cleansed of debris using distilled water after each polishing step. Ultrasonic cleaning was avoided because it could alter the plastic-elastic response of the enamel and loosen their mounting.<sup>[25]</sup>

Each specimen was stored for 24 h before the test in the same ambient environment, which the nano-indentation test was conducted, to reach a stable dry condition so that there were no significant changes during testing.<sup>[25,29]</sup>

#### Nano-indentation test

Nano-indentation testing was performed by the CSM Indentation Tester (Nano-Hardness Tester, CSM, Switzerland) with maximum load of 10 millinewton (10 mN) by a diamond Berkovich indenter tip. Each test included three parts: 10 s for loading to the maximum value, 1 s of holding at the maximum load and 10 s for unloading. The indentations were applied at 1-31  $\mu\text{m}$  depth (7 locations spaced 5  $\mu\text{m}$  apart) from the external enamel surface for the three regions (control, acid-etched and laser-etched regions) on each specimen [Figure 1]. The performer was blind regarding the

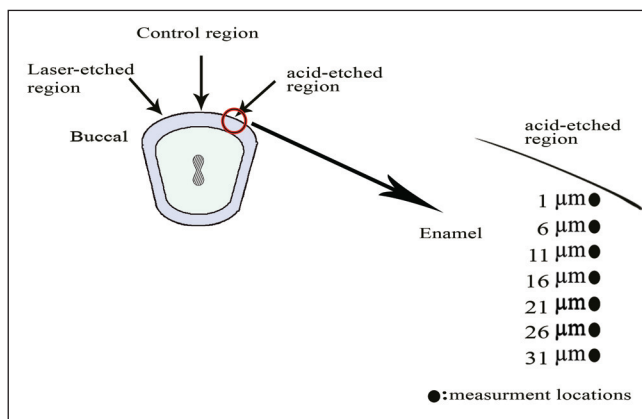

**Figure 1:** The cross-sectional view of the premolar tooth after removing the brackets and residual adhesives, the nano-indentation test was applied at seven locations in each region

type of preparation of each region when recording the amounts of hardness and elastic modulus.


Hardness and elastic modulus were calculated using the software available with the CSM Indentation Tester by Oliver-Pharr method.<sup>[30]</sup> As illustrated in Figure 2, hardness was calculated using maximum force divided by the contact area at maximum load. Elastic modulus was calculated from the slope of the linear portion of the unloading curve at maximum load.<sup>[31]</sup> According to the literature, the Poisson's ratio of 0.28 was assumed for calculating elastic modulus.<sup>[32,33]</sup>

#### Statistical analysis


Both hardness and elastic modulus data were tested for normal distribution and were found to be normally distributed (Kolmogorov-Smirnov test). The mean values of hardness and elastic modulus for the three groups were compared with repeated measure analysis of variance (ANOVA) test followed with the Tukey HSD test and  $P < 0.05$  was considered as significant. The one-way ANOVA was used to compare the hardness and elastic modulus values of the three groups at each of the enamel's depth (1, 6, 11, 16, 21, 26 and 31  $\mu\text{m}$  from the enamel surface). The Tukey HSD test was performed afterward. The results were analyzed using the SPSS software (SPSS Inc., version 16.0, Chicago, IL, USA).

## RESULTS

As illustrated in Figures 3 and 4, mean values for hardness and elastic modulus of the unetched enamel (control group) were 3.22-4.4 GPa and 78.82-92.65 GPa respectively. The enamel etched with laser, showed increased hardness (3.47-6.58 GPa) and elastic modulus values (81.17-116.14 GPa) and the acid-etched enamel showed decreased

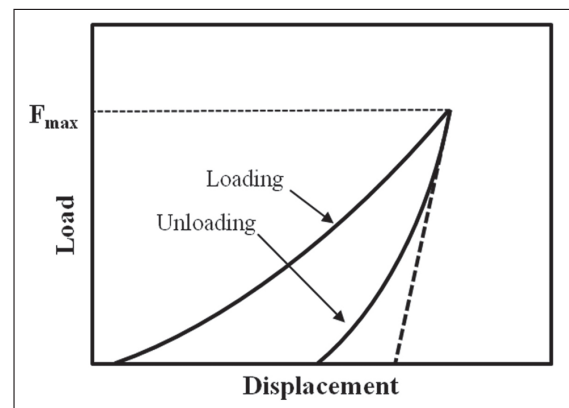

**Figure 2:** Load-displacement curve for a nano-indentation test

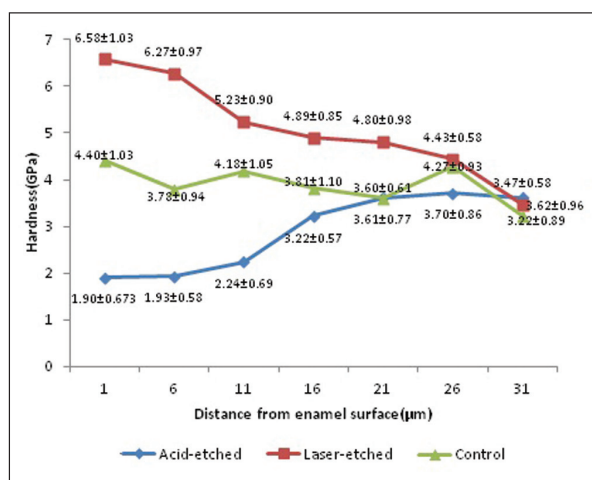

**Figure 3:** Mean values and standard deviations of the hardness of the enamel at different distances from the external surface after bracket de-bonding. Square, laser-etched region; triangle, control region; rhomboid, acid-etched region

hardness (1.90-3.70 GPa) and elastic modulus values (60.24-89.65 GPa).

Repeated measures ANOVA test indicated that three groups (acid-etched, laser-etched and control) were significantly different, regarding hardness and elastic modulus values ( $P < 0.001$ ).


#### Indentation hardness

The hardness values using 1-way ANOVA and *post hoc* Tukey HSD were compared in different enamel's depth (1, 6, 11, 16, 21, 26 and 31 μm from the enamel surface) between three groups and the following results were obtained:

Three groups at locations 1 μm and 6 μm from the enamel surface had significant differences in hardness values ( $P < 0.001$ ). Laser-etched group had higher values than control enamel ( $P < 0.001$ ) and acid-etched group had lower values than control enamel ( $P < 0.001$ ).

At the location 11 μm from the enamel surface, there was significant differences between three groups ( $P < 0.001$ ) and the laser-etched group was significantly harder than the control group ( $P = 0.036$ ). On the contrary, the acid-etched group had significantly lower hardness than the control group ( $P < 0.001$ ).

At the location 16 and 21 μm, the laser-etched enamel had significantly higher hardness than the acid-etched ( $P = 0.001$ ,  $P = 0.007$ , respectively) and unetched enamel ( $P = 0.027$ ,  $P = 0.007$ , respectively). Contrarily, hardness values were not significantly different between acid-etched and control group ( $P = 0.293$ ,  $P = 0.99$ , respectively).

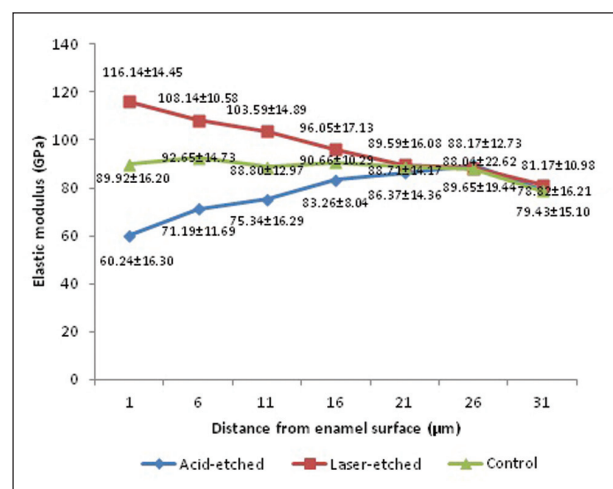

**Figure 4:** Mean values and standard deviations of the elastic modulus of the enamel at different distances from the external surface after bracket de-bonding. Square, laser-etched region; triangle, control region; rhomboid, acid-etched region

Hardness values between three groups were not significantly different at the locations 26 and 31 μm from the enamel surface ( $P = 0.125$ ,  $P = 0.565$ , respectively).

#### Indentation elastic modulus

The elastic modulus values between three groups (laser-etched, acid-etched and control) were evaluated in different locations (1-31 μm from the enamel surface) using one-way ANOVA and Tukey HSD test.

At the location 1 μm and 6 μm from the enamel surface, elastic modulus values had significant differences between the three groups ( $P < 0.001$ ), which elastic modulus values in the laser-etched group were significantly higher than the control enamel ( $P = 0.002$ ,  $P = 0.026$ , respectively) and the acid-etched group had significantly lower elastic modulus than the control group ( $P = 0.001$ ,  $P = 0.002$ , respectively).

In the depth 11 μm from the enamel surface, the laser etched group had significantly higher elastic modulus value than the acid-etched group ( $P = 0.001$ ). Otherwise, elastic modulus values in the acid-etched and laser-etched groups did not have significant differences with the control group ( $P = 0.123$ ,  $P = 0.083$ , respectively).

No statistically significant differences in the elastic modulus were found for the three groups at the locations 16, 21, 26 and 31 μm ( $P = 0.088$ ,  $P = 0.883$ ,  $P = 0.978$ ,  $P = 0.930$ , respectively).

Pearson correlation test indicated that hardness and elastic modulus values were correlated ( $r = 0.58$ ,  $P < 0.001$ ).

## DISCUSSION

In the present study, the hardness values up to 21  $\mu\text{m}$  in depth and elastic modulus values up to 6  $\mu\text{m}$  in depth from the enamel surface for laser-etched enamel were significantly higher than those for unetched enamel. In contrast, the hardness up to 11  $\mu\text{m}$  in depth and elastic modulus up to 6  $\mu\text{m}$  in depth from the enamel surface for phosphoric acid-etched enamel were significantly lower than unetched control enamel.

Iijima *et al.*<sup>[22]</sup> evaluated the effect of bracket bonding on nano-mechanical properties of enamel and reported that the enamel surface at 1 and 5  $\mu\text{m}$  had significantly lower hardness and elastic modulus values in the acid phosphoric etched region compared with the control region, which was similar to our results. Our study also showed the same results for hardness at the 11  $\mu\text{m}$  location, which could be due to higher peak load (10 mN) and higher sample numbers (10 teeth).

Márquez *et al.*<sup>[21]</sup> evaluated effects of Nd:YAG laser using Knoop hardness test on the mechanical properties of the sound enamel and stated that laser application leads to increase the Knoop hardness in all samples. Therefore, their results are similar to ours, but they used the Knoop test for evaluating the hardness, which cannot measure the modulus of elasticity.

In this study, the mean hardness and elastic modulus values for unetched control enamel ranged from 3.22-4.4 GPa and 78.82-92.65 GPa respectively. These values were similar to recent studies using the nano-indentation test.<sup>[23,24,28,32,34]</sup>

Dental enamel contains by volume 85-95% hydroxyapatite crystallites, 8-12% water and 2-3% organic components.<sup>[35]</sup> The hardness and elastic modulus values for the enamel is different for each tooth because the mechanical behaviors vary based on the variation in enamel mineralization, age and health condition of the donors.<sup>[23,36,37]</sup> Moreover, these values may be affected by the location (depth from the enamel surface), applied load, type of indenter, organic components<sup>[34,38]</sup> and orientation of the enamel rods.<sup>[24-26,32]</sup> Thus, these cited factors may explain some variations in the studies.

An established operative technique involves acid etching the enamel surface with a 35-50% solution of

phosphoric acid. This etching produces an irregular and pitted surface with numerous microscopic undercuts by an uneven dissolution of enamel rod heads and tails and leaves the organic rich inter-rod space intact. The composite resin is bonded to the enamel surface by resin tags formed in the acid-etched enamel rod structures. Thus, the mechanical features of the etched enamel surface are affected by penetration of resin tags, high amounts of elastic and soft organic tissue and demineralization.<sup>[22]</sup>

Dickinson *et al.*<sup>[27]</sup> also evaluated nano-mechanical characterization of incipient caries lesions and found that there is a close relation between the low mineral content of lesions and the weak mechanical properties. Moreover, they reported that the lesions with a significant organic content have lower mechanical properties.

The question is what the mechanism of the changes induced by laser is and what is the kind of relation between these changes and increase in the resistance of enamel to decalcification.

Márquez *et al.*<sup>[21]</sup> suggested that laser irradiation could increase the mineralization of the enamel while decreasing the water and organic to inorganic content ratio without affecting the amount of the mineral content.

Also, in previous studies regarding the enamel structural changes induced by Er:YAG laser, these changes were ascribed to the alteration in the mineral composition of the enamel, such as calcium (Ca), phosphorus (P), chlorine and Ca/P ratio,<sup>[39,40]</sup> reduction of carbonate and modification of the organic content.<sup>[41]</sup> On the other hand, Secilmis *et al.*<sup>[42]</sup> found that the mean percentage weights of Ca, P, sodium, potassium and Ca/P ratio of the enamel were not changed by the Er, Cr:YSGG laser irradiation.

There are three theories about the mechanism of acid resistance of enamel treated with laser that could be used for explaining increased hardness and elastic modulus in laser-etched enamel:

1. formation of low soluble compositions, such as tetracalcium diphosphate monoxide,<sup>[17]</sup>
2. melting and recrystallization of enamel surface,<sup>[43]</sup> and
3. alterations in enamel's ultra-structure, such as the decrease of the amount of water and carbonate, increase in the hydroxyl ion contents, formation of pyrophosphates and the breakdown of proteins. These changes occur due to heating the enamel surface up to approximately 650-1100°C during ablation.<sup>[44]</sup>

Although, some investigator have reported that laser creates changes in the morphology of the enamel as cracks and micro-crater like appearance of irradiated surface,<sup>[15,18,39]</sup> which, these cracks in the enamel surface acts as a starting location for fracture during debonding, acid attack and enamel demineralization. Therefore, the positive effect of Er:YAG laser in increasing enamel acid resistance and prevention of caries formation around the orthodontic attachments is decreased or eliminated.<sup>[20]</sup>

We chose nano-indentation test to measure hardness and elastic modulus at multiple locations in the buccal surface of the enamel, because this is an accurate and excellent method to evaluate the mechanical properties of small sub-micrometer volumes of materials.<sup>[34]</sup> The nano-indentation method continuously recorded the load and displacement of the nano-indenter throughout the indentation process, during this process contact area and subsequent mechanical properties are determined automatically, which eliminates the need to image the area of the indentation.<sup>[27]</sup>

The nano-indentation test on the enamel was performed using a 10 mN peak load, which created indentation with about 2  $\mu\text{m}$  width and length thus the 5  $\mu\text{m}$  space eliminated any overlapping between the adjacent indentations.<sup>[24]</sup>

Since a greater peak load produces more stable and accurate values, we used 10 mN maximum loading. In addition, this load allowed that the indentation depth become considerably larger than surface roughness, which minimizes the effect of surface polishing on the values of the hardness and elastic modulus.<sup>[23,24]</sup>

Because the nano-indentation test is performed in an ambient environment over a period of many hours, the samples were kept in a similar dry environment. Although, previous studies reported that the hardness and elastic modulus values obtained from dry enamel were slightly higher than those from wet samples,<sup>[25,29,45]</sup> this enhancement was expected for all specimens and therefore would not influence the data.

The results show that both etching procedures have statistically significant effects on the hardness and elastic modulus values of the enamel surface, but this was an *in vitro* study and the results may be different when the procedures are performed clinically. Further investigations are suggested to clear the mechanism of the effect Er:YAG laser on mechanical properties of the tooth.

## CONCLUSION

Based on the results of present study, the mechanical properties (hardness and elastic modulus) of the enamel surface increased after bracket bonding with Er:YAG laser etching, in contrast, conventional acid etching decreased the hardness and elastic modulus values of the enamel surface as a result of bracket bonding.

## ACKNOWLEDGMENTS

This study was supported by Isfahan University of Medical Sciences Research Grant #390414. The manuscript was based on a thesis submitted to the postgraduate School of Isfahan University of Medical Sciences in partial fulfillment of the Master of Science degree.

## REFERENCES

1. Buonocore MG. A simple method of increasing the adhesion of acrylic filling materials to enamel surfaces. *J Dent Res* 1955;34:849-53.
2. Boyd RL. Comparison of three self-applied topical fluoride preparations for control of decalcification. *Angle Orthod* 1993;63:25-30.
3. Wigdor HA, Walsh JT Jr, Featherstone JD, Visuri SR, Fried D, Waldvogel JL. Lasers in dentistry. *Lasers Surg Med* 1995;16:103-33.
4. Uşümez S, Orhan M, Uşümez A. Laser etching of enamel for direct bonding with an Er, Cr:YSGG hydrokinetic laser system. *Am J Orthod Dentofacial Orthop* 2002;122:649-56.
5. Chung K, Hsu B, Berry T, Hsieh T. Effect of sandblasting on the bond strength of the bondable molar tube bracket. *J Oral Rehabil* 2001;28:418-24.
6. Berk N, Başaran G, Ozer T. Comparison of sandblasting, laser irradiation, and conventional acid etching for orthodontic bonding of molar tubes. *Eur J Orthod* 2008;30:183-9.
7. Olsen ME, Bishara SE, Damon P, Jakobsen JR. Comparison of shear bond strength and surface structure between conventional acid etching and air-abrasion of human enamel. *Am J Orthod Dentofacial Orthop* 1997;112:502-6.
8. Canay S, Kocadereli I, Ak'ca E. The effect of enamel air abrasion on the retention of bonded metallic orthodontic brackets. *Am J Orthod Dentofacial Orthop* 2000;117:15-9.
9. Başaran G, Hamamcı N, Akkurt A. Shear bond strength of bonding to enamel with different laser irradiation distances. *Lasers Med Sci* 2011;26:149-56.
10. Lee BS, Hsieh TT, Lee YL, Lan WH, Hsu YJ, Wen PH, et al. Bond strengths of orthodontic bracket after acid-etched, Er:YAG laser-irradiated and combined treatment on enamel surface. *Angle Orthod* 2003;73:565-70.
11. Ozer T, Başaran G, Berk N. Laser etching of enamel for orthodontic bonding. *Am J Orthod Dentofacial Orthop* 2008;134:193-7.
12. Jamenis SC, Kalia A, Sharif K. Comparative evaluation of shear bond strength of orthodontic bracket using laser etching and

- two conventional etching techniques: An *in vitro* study. J Indian Orthod Soc 2011;45:134-9.
13. Yamamoto H, Ooya K. Potential of yttrium-aluminum-garnet laser in caries prevention. J Oral Pathol 1974;3:7-15.
  14. Bevilacqua FM, Zezell DM, Magnani R, da Ana PA, Eduardo Cde P. Fluoride uptake and acid resistance of enamel irradiated with Er:YAG laser. Lasers Med Sci 2008;23:141-7.
  15. Cecchini RC, Zezell DM, de Oliveira E, de Freitas PM, Eduardo Cde P. Effect of Er:YAG laser on enamel acid resistance: Morphological and atomic spectrometry analysis. Lasers Surg Med 2005;37:366-72.
  16. Oho T, Morioka T. A possible mechanism of acquired acid resistance of human dental enamel by laser irradiation. Caries Res 1990;24:86-92.
  17. Nelson DG, Wefel JS, Jongebloed WL, Featherstone JD. Morphology, histology and crystallography of human dental enamel treated with pulsed low-energy infrared laser radiation. Caries Res 1987;21:411-26.
  18. Souza-Gabriel AE, Chinelatti MA, Borsatto MC, Pécora JD, Palma-Dibb RG, Corona SA. SEM analysis of enamel surface treated by Er:YAG laser: Influence of irradiation distance. Microsc Res Tech 2008;71:536-41.
  19. von Fraunhofer JA, Allen DJ, Orbell GM. Laser etching of enamel for direct bonding. Angle Orthod 1993;63:73-6.
  20. Apel C, Meister J, Götz H, Duschner H, Gutknecht N. Structural changes in human dental enamel after subablative erbium laser irradiation and its potential use for caries prevention. Caries Res 2005;39:65-70.
  21. Márquez F, Quintana E, Roca I, Salgado J. Physical-mechanical effects of Nd:YAG laser on the surface of sound dental enamel. Biomaterials 1993;14:313-6.
  22. Iijima M, Muguruma T, Brantley WA, Ito S, Yuasa T, Saito T, et al. Effect of bracket bonding on nanomechanical properties of enamel. Am J Orthod Dentofacial Orthop 2010;138:735-40.
  23. Hairul Nizam BR, Lim CT, Chng HK, Yap AU. Nanoindentation study of human premolars subjected to bleaching agent. J Biomech 2005;38:2204-11.
  24. Kohda N, Iijima M, Brantley W, Muguruma T, Yuasa T, Nakagaki S, et al. Effects of bonding materials on the mechanical properties of enamel around orthodontic brackets. Angle Orthod 2012;82:187-95.
  25. Cuy JL, Mann AB, Livi KJ, Teaford MF, Weihs TP. Nanoindentation mapping of the mechanical properties of human molar tooth enamel. Arch Oral Biol 2002;47:281-91.
  26. Ang SF, Scholz T, Klocke A, Schneider GA. Determination of the elastic/plastic transition of human enamel by nanoindentation. Dent Mater 2009;25:1403-10.
  27. Dickinson ME, Wolf KV, Mann AB. Nanomechanical and chemical characterization of incipient *in vitro* carious lesions in human dental enamel. Arch Oral Biol 2007;52:753-60.
  28. Habelitz S, Marshall GW Jr, Balooch M, Marshall SJ. Nanoindentation and storage of teeth. J Biomech 2002;35:995-8.
  29. Zhou J, Hsiung LL. Depth-dependent mechanical properties of enamel by nanoindentation. J Biomed Mater Res A 2007;81:66-74.
  30. Oliver WC, Pharr GM. An improved technique for determining hardness and elastic modulus using load and displacement sensing indentation experiments. J Mater Res 1992;7:1564-83.
  31. Doerner MF, Nix WD. A method for interpreting the data from depth-sensing indentation instruments. J Mater Res 1986;1:601-9.
  32. Habelitz S, Marshall SJ, Marshall GW Jr, Balooch M. Mechanical properties of human dental enamel on the nanometre scale. Arch Oral Biol 2001;46:173-83.
  33. Waters NE. Some mechanical and physical properties of teeth. Symp Soc Exp Biol 1980;34:99-135.
  34. He LH, Swain MV. Influence of environment on the mechanical behaviour of mature human enamel. Biomaterials 2007;28:4512-20.
  35. Gwinnett AJ. Structure and composition of enamel. Oper Dent 1992;Suppl 5:10-7.
  36. Kinney JH, Balooch M, Marshall GW, Marshall SJ. A micromechanics model of the elastic properties of human dentine. Arch Oral Biol 1999;44:813-22.
  37. Mahoney E, Holt A, Swain M, Kilpatrick N. The hardness and modulus of elasticity of primary molar teeth: An ultra-micro-indentation study. J Dent 2000;28:589-94.
  38. Baldassarri M, Margolis HC, Beniash E. Compositional determinants of mechanical properties of enamel. J Dent Res 2008;87:645-9.
  39. Rodríguez-Vilchis LE, Contreras-Bulnes R, Olea-Mejía OF, Sánchez-Flores I, Centeno-Pedraza C. Morphological and structural changes on human dental enamel after Er:YAG laser irradiation: AFM, SEM, and EDS evaluation. Photomed Laser Surg 2011;29:493-500.
  40. Mine A, Yoshida Y, Suzuki K, Nakayama Y, Yatani H, Kuboki T. Spectroscopic characterization of enamel surfaces irradiated with Er:YAG laser. Dent Mater J 2006;25:214-8.
  41. Liu Y, Hsu CY. Laser-induced compositional changes on enamel: A FT-Raman study. J Dent 2007;35:226-30.
  42. Secilmis A, Usumez A, Usumez S, Berk G. Evaluation of mineral content of enamel prepared by erbium, chromium:yttrium-scandium-gallium-garnet laser. Lasers Med Sci 2010;25:467-72.
  43. Stern RH, Sognaes RF, Goodman F. Laser effect on *in vitro* enamel permeability and solubility. J Am Dent Assoc 1966;73:838-43.
  44. Fowler BO, Kuroda S. Changes in heated and in laser-irradiated human tooth enamel and their probable effects on solubility. Calcif Tissue Int 1986;38:197-208.
  45. Staines M, Robinson WH, Hood JA. Spherical indentation of tooth enamel. J Mater Sci 1981;16:2551-6.

**How to cite this article:** Alavi S, Birang R, Hajizadeh F, Banimostafae H. Effect of bracket bonding with Er: YAG laser on nanomechanical properties of enamel. Dent Res J 2014;11:49-55.

**Source of Support:** This report is based on a thesis which was submitted to the School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran, in partial fulfillment of the requirements for the MSc degree in Orthodontics (#390414). The study was approved by the Medical Ethics and Research Office at the Isfahan University of Medical Sciences and financially supported by this University.

**Conflict of Interest:** None declared.